

First-Principles Computations for KTN

S. Prosandeev^{1,2}, E. Cockayne¹, B. Burton¹ and A. Turik²

¹National Institute of Standards and Technology, MD; ²Rostov State University

Solid solutions of KTaO_3 and KNbO_3 (KTN) exhibit unusual dielectric properties at ferroelectric phase transitions, which are usually associated with a Nb instability [1] that is often explained by the large Nb dynamical charge in oxides. Using non-self-consistent VASP computations [2], we showed earlier that the Nb dynamical charge in layered KTN strongly depends on the local environment of Nb. In the present study, we have performed self-consistent first-principles computations for fixed composition $\text{KTa}_{7/8}\text{Nb}_{1/8}\text{O}_3$ in different configurations shown in Fig. 1. We computed the equilibrium ionic positions, Born charges, force constants, vibration frequencies and modes.

In agreement with our previous results, we found that the Nb dynamical charge is sensitive to the nearest neighbors (Table 1). The Nb charge in directions where there are only Nb ions is about 9.9e. In the direction where there are Ta ions, the Nb dynamical charge is about 8.3e. In contrast, the Ta charge increases in directions where there are Nb ions. The comparison of the energies (Table 2) shows that there is tendency to Nb ordering in planes if one does not take into account external stress necessary for obtaining experimental lattice constant in KTaO_3 . When we applied this stress, we obtained that the energies of the considered structures are close to each other. Note that this situation is very different from that known for PST, PMN etc.: in those cases, 1:1 or 1:2 order appears as a result of electrostatic interactions due to different charges of Nb and Mg or Sc and Ta [3]. In KTN, the valence of Nb and Ta is the same.

TABLE I: Ta and Nb dynamical charges in KTN 181. The numbers correspond to the Ta ions from the left to the right (Fig. 1).

	x	y	z		x	y	z
1Ta	8.758	8.938	8.758	2Ta	8.755	9.009	8.755
3Ta	8.753	9.017	8.753	4Ta	8.752	9.017	8.752
5Ta	8.753	9.017	8.753	6Ta	8.755	9.009	8.755
7Ta	8.758	8.938	8.758	Nb	9.898	8.259	9.898

We obtained that the average Nb-O distance is larger than the average Ta-O distance. It implies that the Nb ions cause tensile distortion in KTN. Nevertheless, the lowest soft TO modes are mostly due to Nb (Table 3).

We also found that the lattice instability in the KTN 181 configuration appears in the directions of the Nb planes. That is consistent with other first-principles computations [4]. The instabilities can be explained by

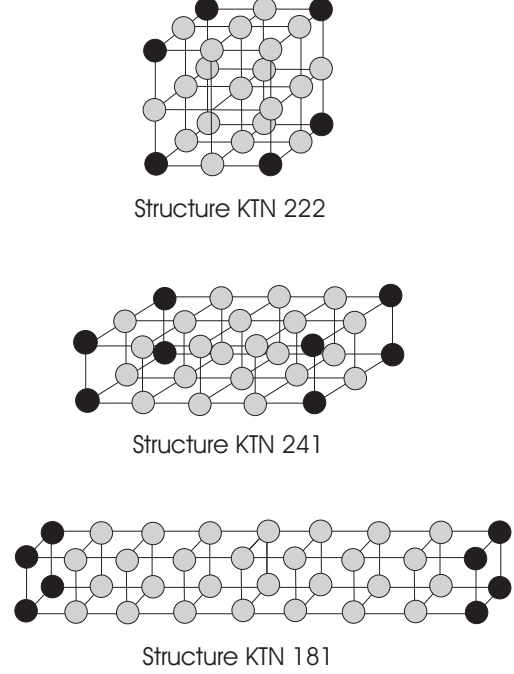


FIG. 1: The geometry of the structures considered.

TABLE II: Total energies (with respect to the highest value obtained) for the computed supercells [eV]. “equilibr.” is the self-consistent energy obtained at zero stress. “Vegard” is the energy obtained at the volume which is the average between KTaO_3 and KNbO_3 . “KT-stress” is the energy obtained at the hydrostatic stress giving experimental lattice constant for KTaO_3 .

structure	KTN222	KTN181	KTN241
equilibr.	-0.08082	-0.38057	-0.08071
Vegard	-0.06353	-0.32842	-0.06334
KT-stress	-0.00250	-0.00000	

the long-range dipole-dipole interaction supplemented by the covalent (pseudo vibronic) effect: the displacement of one of the Nb ions along the Nb-O-Nb bond triggers appearing an additional force on nearest Nb ions in the same chain due to the change of electronic structure that is produced by the shift of the Nb ion [5]: $\varepsilon_{cor}(R_1, R_2) = \sum_{\tau, \tau'} [W(R_1)_{\tau, \tau'} W(R_2)_{\tau', \tau}] f^\tau (1 - f^{\tau'}) / [\varepsilon^\tau - \varepsilon^{\tau'}]$ where

TABLE III: Vibration frequencies obtained for TO1 soft modes [cm^{-1}] at the external stress corresponding to an experimental lattice constant in KTaO_3 .

KTN 222		KTN 181	
ν		ν	
44, 54	x	8i, 30	z
44, 54	y	8i, 30,	x
44, 54	z	35, 41	y

$W(R) = r(\partial H/\partial R)$ is the linear vibronic operator, r being the ionic displacement and H being the electron Hamiltonian, ε^τ , f^τ are electron energy and occupation number, respectively, τ denotes the electronic state.

By using a tight-binding approach [5, 6] we have computed the correlation energy for the ionic displacements in KNbO_3 , in $(z^2/R_{\text{Nb-O}}^2)\text{eV}$ units, where z being the ionic charge and $R = R_{\text{Nb-O}}$ is the Nb-O bond length. When the nearest Nb ions are shifted, the correlation energy is -10.3 and -0.9 for the displacements along and perpendicular to the Nb-O-Nb line, respectively. If Nb and nearest O are shifted then the correlation energy is 25.9 and 8.6 for the displacements along and perpendicular to the Nb-O bond, respectively. Hence, the vibronic effect facilitates the displacement of the Nb ions in the chains in the same direction while the Nb and O ions are easily shifted in opposite directions. This result is in qualitative agreement with straightforward computations of the interatomic force constants (see [7] and references therein), which showed that the M-O force constant along the $\dots\text{M-O-M-O}\dots$ chains proves to be practically negligible while the M-M force constant appears to be surprisingly strong.

Hence, the local polarization in KTN appears in the Nb-reached regions. The polarization direction follows the field and the free energy can be written as: $F = \alpha(P - P_0)^2 + A(P - P_0)^3 + \dots - (E + E_0)P$ where E_0 is random and P is polarization *magnitude* ($P > P_0 > 0$ where P_0 is the lowest possible, remnant, magnitude of polarization). An unusual field dependence of susceptibility follows from this: $1/\chi(E) = 2\alpha + 3AE/\alpha + \dots$, $E \gg E_0$. At smaller fields, susceptibility is constant or decreases because of averaging over E_0 [8].

The strongly angle dependent correlation of the displacements can explain the diffuse X-ray scattering in KNbO_3 [9] without the assumption that the Nb ions have *deep* off-center wells. At high temperatures (where the soft mode is stabilized), acoustic excitations of the (Nb or O) chains can be intensive due to nearly flat transverse acoustic phonon energy surface in (001) planes [10]. The peaks in the XANES data [11] can be understood if the large chain-like fluctuations are considered together with the strong dependence of the X-Ray absorption matrix element on the ionic displacements [12].

The dynamical nature of the cooperative displacements [13] is supported by the fact that, in the high temperature cubic phase, there is little dielectric dispersion [14]. In the ferroelectric phases, the situation is more complicated. For instance, in the tetragonal phase, the average polarization is directed along the [001] direction. However, the direction of a local Nb displacement is [111] due to anharmonicity. The correlation of the displacements can result in the appearance of finite size chains directed in the [001] directions, while the metal ions are displaced in [111] directions (common within a finite-size chain but random in different chains [13]). One can introduce population numbers for such chains corresponding to different directions of the displacements. Note that these (quasistatic) chains can exist only because of i) anharmonicity of the potential relief, where the direction of the (local) displacement does not coincide with the direction of the polarization, ii) strong correlation of the displacements, iii) existence of a uniform macroscopic field. In the cubic phase, the last condition fails and the dispersion connected with the chains disappears. In PbTiO_3 , the low-temperature phase is tetragonal: the ions are shifted in the [001] direction and the first condition fails; the dispersion is also absent in accordance with experiment [14]. In the ferroelectric phases of BaTiO_3 and KNbO_3 , all three conditions are satisfied and the dispersion exists [14].

-
- [1] W. Kleemann, F.J. Schafer and D. Rytz, Phys. Rev. Lett. **54**, 2038 (1985).
 - [2] S. Prosandeev, E. Cockayne, and B. Burton, AIP Conference Proceedings **626**, 64 (2002); cond-mat/0208316.
 - [3] B.P. Burton and E. Cockayne Phys. Rev. B **60**, R12542 (1999).
 - [4] M. Sepliarsky, S.R. Phillpot, D. Wolf, M.G. Stachiotti and R.L. Migoni, J. Appl. Phys. **90**, 4509 (2001).
 - [5] W.A. Harrison, Electronic structure and properties of solids, Ed. W.H. Freeman & Co., San Francisco 1980.
 - [6] S.A. Prosandeev and A.A. Nerodo, Izv. ANSSR, ser. fiz. **57**, 73 (1993).
 - [7] S. Tinte, M.G. Stachiotti, M. Sepliarsky, R.L. Migoni and C.O. Rodriguez, J. Phys.: Condens. Matter **11**, 9679 (1999).
 - [8] S.A. Prosandeev, Phys. Sol. St. **45** 1774 (2003).
 - [9] R. Comes, M. Lambert and A. Guinier. Acta Cryst. **A26**, 244 (1970).
 - [10] B. Dorner and R. Comes, in Dynamics of Solids and Liquids by Neutron Scattering, ed. S.W. Lovesey and T. Springer, Springer-Verlag, Berlin, 1977.
 - [11] B. Ravel, E.A. Stern, Physica B, **208/209**, 316 (1995).
 - [12] R.V. Vedrinskii, V.L. Kraizman, A.A. Novakovich, Ph.V. Demekhin and S.V. Urazhdin, J. Phys.: Condens. Matter **10**, 9561 (1998).
 - [13] H. Takahasi, J. Phys. Soc. Jap. **16**, 1685 (1961).
 - [14] A.V. Turik, Ferroelectrics **221**, 111 (1999).